

*Scaling of the superfluid density in high-temperature
superconductors*

C.C. Homes

Presented at the 18th International Symposium on Superconductivity (ISS2005)
Tsukuba, Japan
October 24-26, 2005

Condensed Matter Physics/Materials Science Department (CMP/MSD)
Brookhaven National Laboratory
P.O. Box 5000
Upton, NY 11973-5000
www.bnl.gov

Notice: This manuscript has been authored by employees of Brookhaven Science Associates, LLC under Contract No. DE-AC02-98CH10886 with the U.S. Department of Energy. The publisher by accepting the manuscript for publication acknowledges that the United States Government retains a non-exclusive, paid-up, irrevocable, world-wide license to publish or reproduce the published form of this manuscript, or allow others to do so, for United States Government purposes.

This preprint is intended for publication in a journal or proceedings. Since changes may be made before publication, it may not be cited or reproduced without the author's permission.

DISCLAIMER

This report was prepared as an account of work sponsored by an agency of the United States Government. Neither the United States Government nor any agency thereof, nor any of their employees, nor any of their contractors, subcontractors, or their employees, makes any warranty, express or implied, or assumes any legal liability or responsibility for the accuracy, completeness, or any third party's use or the results of such use of any information, apparatus, product, or process disclosed, or represents that its use would not infringe privately owned rights. Reference herein to any specific commercial product, process, or service by trade name, trademark, manufacturer, or otherwise, does not necessarily constitute or imply its endorsement, recommendation, or favoring by the United States Government or any agency thereof or its contractors or subcontractors. The views and opinions of authors expressed herein do not necessarily state or reflect those of the United States Government or any agency thereof.

Scaling of the superfluid density in high-temperature superconductors

C. C. Homes *

*Department of Condensed Matter Physics and Materials Science, Brookhaven
National Laboratory, Upton, New York, 11973*

Abstract

A scaling relation $N_c \simeq 4.4 \sigma_{dc} T_c$ has been observed parallel and perpendicular to the copper-oxygen planes in the high-temperature superconductors; N_c is the spectral weight and σ_{dc} is the dc conductivity just above the critical temperature T_c . In addition, Nb and Pb also fall close to the this scaling line. The application of the Ferrell-Glover-Tinkham sum rule to the BCS optical properties of Nb above and below T_c yields $N_c \simeq 8.1 \sigma_{dc} T_c$ when the normal-state scattering rate is much greater than the superconducting energy gap ($1/\tau > 2\Delta$, the “dirty” limit). This result implies that the high-temperature superconductors may be in the dirty limit. The superconductivity perpendicular to the planes is explained by the Josephson effect, which again yields $N_c \simeq 8.1 \sigma_{dc} T_c$ in the BCS formalism. The similar forms for the scaling relation in these two directions suggests that in some regime the dirty limit and the Josephson effect may be viewed as equivalent.

Key words: Infrared, superconductivity, spectral weight, scaling

PACS: 74.25.Gz, 74.25.-q, 74.72.-h, 72.15.Lh

1 Introduction

Scaling laws express a systematic and universal simplicity in nature. In complex biological systems, scaling laws can be tremendously useful [1], and they are equally important in the physical sciences. Since the discovery of superconductivity at elevated temperatures in copper-oxide materials some 20 years ago [2], there has been considerable effort to identify trends and correlations between the physical quantities as a clue to the origin of the superconductivity [3]. One of the earliest patterns that emerged was the linear scaling of the superfluid density ρ_s in the copper-oxygen planes of the hole-doped materials with the superconducting transition temperature T_c (where ρ_s is proportional to the number of carriers in the condensate n_s ; in addition $\rho_s \propto 1/\lambda^2$, where λ is the superconducting penetration depth). This is the celebrated Uemura relation [4,5] and it works well for the underdoped materials. However, this relation appears to break down in the very underdoped [6] and overdoped [7,8] materials (optimal doping is defined where T_c is a maximum [9]).

In contrast, we have recently demonstrated a scaling relation $N_c \simeq 4.4 \sigma_{dc} T_c$ [10,11], where N_c is the spectral weight of the condensate ($N_c = \rho_s/8$) and σ_{dc} is the dc conductivity just above the critical temperature. (In this instance both sides of the equation possess the same units, so that the constant is

* Tel.: 631 344 7579, fax: 631 344 2739

Email address: homes@bnl.gov (C. C. Homes).

dimensionless. The dimensionless constant and the description of the scaling in terms of N_c rather than ρ_s results in a prefactor which is smaller than observed in our previous work [10]). This relation appears to hold regardless of the doping level or type, nature of the disorder, or direction (along or perpendicular to the copper-oxygen planes). In addition to the copper-oxide materials, the simple elemental BCS superconductors Nb and Pb are also observed to follow this relation. The optical properties of Nb were calculated in the normal and superconducting states. The spectral weight N_c is then determined from conductivity sum rules. The linear scaling $N_c \propto \sigma_{dc} T_c$ is recovered in the BCS “dirty” limit $1/\tau > 2\Delta$, where $1/\tau$ is the normal-state scattering rate and 2Δ is the isotropic BCS superconducting energy gap ($T \ll T_c$). This result suggests that the copper-oxide materials may be in the “dirty” limit. The superconductivity perpendicular to the planes is thought to arise from Josephson coupling; interestingly, this approach again yields the scaling relation $N_c \propto \sigma_{dc} T_c$ [11]. This result and a possible connection with the in-plane behavior is discussed.

2 Experiment and Results

The relevant experimental quantities here are the spectral weight of the condensate ($N_c \propto 1/\lambda^2$) for $T \ll T_c$ and σ_{dc} at $T \simeq T_c$. Normally, these two quantities are determined using different experimental techniques on different samples where the dopings are at best similar, but never identical. A fundamental advantage of optical reflectance techniques is that the real and imaginary parts of the dielectric function $\tilde{\epsilon} = \epsilon_1 + i\epsilon_2$ may be determined, allowing both N_c and σ_{dc} to be calculated for the same sample. The reflectance

of a large number of single and double layer cuprates has been measured over a wide frequency range by a number of different workers, and the Kramers-Kronig analysis used to calculate the complex optical properties [12]. The real part of the optical conductivity is $\sigma_1(\omega) = -i\omega\epsilon_2/4\pi$ (in units of cm^{-1}), and $\sigma_{dc} = \sigma_1(\omega \rightarrow 0)$ at $T \simeq T_c$. For $T \ll T_c$, the response of $\tilde{\epsilon}$ to the formation of a superconducting condensate is ideally purely real, thus $\epsilon_1 = \epsilon_\infty - \omega_{ps}^2/\omega^2$, and $\omega_{ps}^2 = -\omega^2\epsilon_1(\omega)$ in the $\omega \rightarrow 0$ limit. Here, $\omega_{ps}^2 = 4\pi n_s e^2/m^*$ is the square of the superconducting plasma frequency, n_s is the superconducting carrier concentration, m^* is an effective mass, and ϵ_∞ is the high-frequency contribution to the real part of the dielectric function. The strength of the condensate is simply $\rho_s \equiv \omega_{ps}^2$, which is proportional to n_s/m^* . The value of ρ_s may also be estimated by examining the changes in the optical conductivity just above and well below T_c . The f -sum rule for the conductivity [13] has the form $\int_0^\infty \sigma_1(\omega) d\omega = \omega_p^2/8$, where $\omega_p^2 = 4\pi n e^2/m$ is the classical plasma frequency. The spectral weight at a given cut-off frequency ω_c is defined here as

$$N(\omega_c, T) = \int_{0^+}^{\omega_c} \sigma_1(\omega, T) d\omega, \quad (1)$$

which is simply the area under the conductivity curve. The copper-oxide materials, and superconductors in general, show a dramatic suppression of the low-frequency conductivity upon entering the superconducting state; this difference between the $T \simeq T_c$ and $T \ll T_c$ conductivities is often referred to as the “missing area”. The spectral weight associated with the formation of the superconducting condensate is then $N_c = N_n - N_s$, where $N_n \equiv N(\omega_c, T \simeq T_c)$, and $N_s \equiv N(\omega_c, T \ll T_c)$, and ω_c is chosen such that N_c converges. Here, N_c is simply the spectral weight associated with the missing area in the conduc-

tivity, which is related to the square of the superconducting plasma frequency

$$\omega_{ps}^2 = 8 N_c, \quad (2)$$

or $\rho_s = 8 N_c$. This expression is the well-known Ferrell-Glover-Tinkham sum rule [14,15]. These two different techniques typically yield nearly identical values for ρ_s ; an exception exists in the underdoped materials perpendicular to the planes, where it has been suggested that there is missing spectral weight [16]. The optically-determined values of ω_{ps} , σ_{dc} and T_c [17] for a wide variety of copper-oxygen superconductors are listed in Table I of Ref. [12], and are shown in the log-log plot of Fig. 1. Within error, all of the points may be described by the relation $N_c \simeq 4.4 \sigma_{dc} T_c$.

3 Discussion

In addition to the copper-oxide superconductors, the elemental BCS superconductors Pb and Nb also fall very close to the scaling line shown in Fig. 1. This is surprising because unlike BCS superconductors which have nearly isotropic s -wave energy gaps, the copper-oxide materials are thought to possess gaps which are d wave in nature and contain nodes [18,19]. A gap with $d_{x^2-y^2}$ symmetry may be written as $\Delta_k = \Delta_0 [\cos(k_x a) - \cos(k_y a)]$; the gap reaches a maximum at the $(0, \pi)$ and $(\pi, 0)$ points, and vanishes along the nodal (π, π) directions. A deeper understanding of the scaling relation as it relates to both the elemental superconductors and the copper-oxide materials may be obtained from an examination of the spectral weight above and below T_c in relation to the normal-state scattering rate and the superconducting energy gap.

In order to achieve this, the optical properties for Nb have been calculated in both the normal and superconducting states. The “metallic” normal state may be described by the Drude model where the complex dielectric function is

$$\tilde{\epsilon}(\omega) = \epsilon_{\infty} - \frac{\omega_p^2}{\omega(\omega + i\gamma)}, \quad (3)$$

ϵ_{∞} and the ω_p have been previously defined, and $\gamma = 1/\tau$. The dielectric function and the conductivity are related through $\tilde{\sigma} = \sigma_1 + i\sigma_2 = -i\omega(\tilde{\epsilon} - \epsilon_{\infty})/4\pi$. Thus $\sigma_1 = \sigma_{dc}/(1 + \omega^2\tau^2)$ with $\sigma_{dc} = \omega_p^2\tau/4\pi$ (in units of cm^{-1}), which has the shape of a Lorentzian centered a zero frequency, with a width of $1/\tau$. The plasma frequency for Nb has been taken to be $\omega_p = 56\,000\text{ cm}^{-1}$ [20]. The behavior of Nb in the superconducting state has been modeled using the BCS model [21] for an arbitrary purity level with a critical temperature of $T_c = 9.2\text{ K}$ and a gap of $2\Delta = 22.3\text{ cm}^{-1}$ (the BCS weak-coupling limit $2\Delta = 3.5 k_B T_c$); a wide range of of normal-state scattering rates $1/\tau = 0.05\Delta \rightarrow 50\Delta$ have been examined. The spectral weight of the condensate N_c has been determined by integrating to $\omega_c \simeq 200\Delta$; N_c is observed to converge smoothly for all the values of $1/\tau$ examined. The result of this calculation is shown as the solid line in Fig. 2, and the vertical dashed line indicates where $1/\tau = 2\Delta$. The point to the right of the dashed line is for Nb recrystallized in ultra-high vacuum [22] to achieve conditions in which the residual resistivity ratios $[\rho(\text{RT})/\rho(T \gtrsim T_c)]$ are well in excess of 100, and where $N_c \rightarrow \omega_p^2/8$ (or $\rho_s \rightarrow \omega_p^2$) for $T \ll T_c$. As the scattering rate increases the strength of the condensate begins to decrease until it adopts the linear scaling behavior $N_c \simeq 8.1 \sigma_{dc} T_c$ observed in Fig. 2. (It should be noted that the BCS model yields the same asymptotic behavior in the dirty limit, regardless of the choice of ω_p or Δ ; the

constant is only sensitive upon the ratio of Δ to T_c .) The two points for Nb shown in Fig. 1 [23,24], (reproduced in Fig. 2), fall close to this line and are clearly in the dirty limit. Thus, the scaling relation N_c or $\rho_s \propto \sigma_{dc} T_c$ is the hallmark of a BCS dirty-limit system [25]. The presence of σ_{dc} in the scaling relation indicates the nature of the superconductivity depends on the normal-state scattering rate. To illustrate this point more clearly, we consider the two extreme limits in Fig. 2; the clean and dirty limits.

The clean limit case ($1/\tau \ll 2\Delta$) is illustrated in Fig. 3 for the choice $1/\tau = 0.2\Delta$. Nearly all of the spectral weight associated with the condensate lies below 2Δ . As a result, the normalized spectral weight of the condensate $8 N_c/\rho_s$ (the difference in the area under the two curves indicated by the hatched region) shown in the inset of Fig. 3, approaches unity at frequencies closer to $1/\tau$ rather than 2Δ . The spectral weight for the condensate may be estimated simply as a geometric area $N_c \simeq \sigma_{dc}/\tau$. If $1/\tau \propto T_c$ for $T \simeq T_c$ in the copper-oxide materials [26], then $N_c \propto \sigma_{dc} T_c$, in agreement with the observed scaling relation. It is interesting to note that $1/\tau \propto T_c$ may yield rather large values for the normal-state scattering rate, and it has been suggested that the copper-oxide materials are close to the maximum level of dissipation allowed for these systems [27]. In addition, to achieve the clean limit it is not only necessary that $1/\tau \ll 2\Delta_0$, but also that $1/\tau \lesssim 2\Delta_k$ in the nodal regions. The clean-limit requirement is much more stringent for a d -wave system than it is for a material with an isotropic energy gap, and it is not clear that it will ever be satisfied in the copper-oxide superconductors. This suggests that a dirty-limit view may be more appropriate. It should be emphasized at this point that in the high-temperature superconductors the large normal-state scattering rate is not due to impurities, but rather from out-of-plane disorder,

correlation effects, or a combination of both.

The BCS dirty limit ($1/\tau > 2\Delta$) is shown in Fig. 4 for the choice of $1/\tau = 10\Delta$. In this case the normal-state conductivity is a broadened Lorentzian, and much of the spectral weight has been pushed out above 2Δ . As a result, the normalized spectral weight of the condensate, shown in the inset, converges much more slowly than in the clean-limit case. However, a majority of the spectral weight is captured by 2Δ and N_c is almost fully formed above 4Δ . In this case, the spectral weight of the condensate (the hatched area in Fig. 4) may be estimated as $N_c \simeq \sigma_{dc} 2\Delta$. In the BCS model, the energy gap 2Δ scales linearly with T_c , yielding $N_c \propto \sigma_{dc} T_c$, which is in agreement with the observed scaling relation. This result necessarily implies that the energy scale for the condensate is proportional to T_c .

The scaling relation predicted by the BCS model has a numerical constant of 8.1, but the geometrical estimate assuming weak coupling yields a value of only 2.4. An examination of Fig. 4 indicates that this discrepancy arises from the fact that $N_c \simeq \sigma_{dc} 2\Delta$ underestimates the spectral weight by more than a factor of two. The results from Fig. 2 suggest that a more realistic estimate of the area is $N_c \simeq 3.3(\sigma_{dc} 2\Delta)$, which assuming weak coupling yields the correct numerical constant in the scaling relation. The observed scaling relation in the cuprates would imply that $2\Delta/k_B T_c \simeq 2$. However, this statement suffers from the fact that it is valid only within a BCS formalism for an isotropic s -wave gap. Another, perhaps more reasonable, explanation for the different numerical constants between the BCS and high-temperature superconductors may arise from the fact that copper-oxide superconductors have nodes in the energy gap, and as a consequence there is still a substantial amount of low-frequency residual conductivity at low temperature [28] resulting in a reduced

estimate for the spectral weight for the condensate.

It was previously noted [10] that the scaling relation $N_c \simeq 4.4 \sigma_{dc} T_c$ is a universal result that describes not only the copper-oxygen (a - b) planes, but perpendicular to the planes (c axis) as well, as shown in Fig. 5. While a description of the scaling based on scattering rates within the context of clean and dirty limits may be appropriate for the a - b planes where the transport is coherent, it is inappropriate along the c axis, where the activated nature of the temperature dependence of the resistivity indicates that the transport in this direction is incoherent and governed by hopping [29]. In this case, the superconductivity along the c axis may be described by the Josephson effect, which for the BCS weak coupling case ($2\Delta = 3.5 k_B T_c$) yields $N_c \simeq 8.1 \sigma_{dc} T_c$ [11]. Surprisingly, this is precisely the result that was obtained in the a - b planes for the BCS weak-coupling case in the dirty limit in Fig. 2, indicating that from a functional point of view the scaling behavior of the dirty limit and the Josephson effect are nearly identical. Because these calculations have all been done using a BCS formalism, there is some uncertainty in applying these results to d -wave systems. It is possible that the Josephson effect arises naturally out of systems with an increasing amount of disorder and as a result any crossover from coherent to incoherent behavior still yields the same form of the scaling relation. The dynamical nature of the electronic inhomogeneities in the copper-oxygen planes may support this argument [30].

4 Conclusions

The implications of the linear scaling relation N_c or $\rho_s \propto \sigma_{dc} T_c$ in the copper-oxide superconductors have been examined within the context of clean and

dirty-limit systems. In the conventional BCS superconductors (such as Nb), this linear scaling is the hallmark of a dirty-limit superconductor. The copper-oxide materials are thought to be *d*-wave superconductors, in which the clean limit is difficult to achieve. The observed linear scaling strongly suggests that the copper-oxide superconductors are either close to or in the dirty limit. Estimates of N_c (or ρ_s) based on geometric arguments imply that the energy scale below which the majority of the spectral weight is transferred into the condensate scales linearly with T_c . The *a-b* planes and the *c* axis follow the same scaling relation. The scaling behavior for the dirty limit and the Josephson effect (assuming a BCS formalism) is essentially identical from a functional point of view, suggesting that in some regime the dirty limit and the Josephson effect may be viewed as equivalent.

5 Acknowledgements

It is a pleasure to acknowledge many useful discussions with thank Y. Ando, D. N. Basov, D. A. Bonn, I. Bozovic, A. V. Chubukov, S. V. Dordevic, M. Greven, W. N. Hardy, P. D. Johnson, S. A. Kivelson, P. A. Lee, T. M. Rice, M. Strongin, D. B. Tanner, T. Timusk, J. J. Tu and T. Valla. Work at Brookhaven was supported by the DOE under contract number DE-AC02-98CH10886.

References

- [1] J. H. Brown, G. B. West (Eds.), *Scaling in biology*, Oxford University Press, Oxford, 1999.
- [2] J. G. Bednorz, K. A. Müller, *Z. Phys. B* 64 (1986) 189.

- [3] T. Schneider, *Europhys. Lett.* 60 (2002) 141.
- [4] Y. J. Uemura, G. M. Luke, B. J. Sternlieb, J. H. Brewer, J. F. Carolan, W. N. Hardy, R. Kadono, R. F. Kiefl, S. R. Kreitzman, P. Mulhern, T. M. Riseman, D. L. Williams, B. X. Yang, S. Uchida, H. Takagi, J. Gopalakrishnan, A. W. Sleight, M. A. Subramanian, C. L. Chien, M. Z. Cieplak, G. Xiao, V. Y. Lee, B. W. Statt, C. E. Stronach, W. J. Kossler, X. H. Yu, *Phys. Rev. Lett.* 62 (1989) 2317.
- [5] Y. J. Uemura, L. P. Le, G. M. Luke, B. J. Sternlieb, W. D. Wu, J. H. Brewer, T. M. Riseman, C. L. Seaman, M. B. Maple, M. Ishikawa, D. G. Hinks, J. D. Jorgensen, G. Saito, H. Yamochi, *Phys. Rev. Lett.* 66 (1991) 2665.
- [6] Y. Zuev, M. S. Kim, T. R. Lemberger, *Phys. Rev. Lett.* 95 (2005) 137002.
- [7] C. Niedermayer, C. Bernhard, U. Binninger, H. Glückler, J. L. Tallon, E. J. Ansaldo, J. I. Budnick, *Phys. Rev. Lett.* 71 (1993) 1764.
- [8] J. L. Tallon, J. W. Loram, J. R. Cooper, C. Panagopoulos, C. Bernhard, *Phys. Rev. B* 68 (2003) 180501.
- [9] M. R. Presland, J. L. Tallon, R. G. Buckley, R. S. Liu, N. E. Flower, *Physica C* 176 (1991) 95.
- [10] C. C. Homes, S. V. Dordevic, M. Strongin, D. A. Bonn, R. Liang, W. N. Hardy, S. Komiya, Y. Ando, G. Yu, N. Kaneko, X. Zhao, M. Greven, D. N. Basov, T. Timusk, *Nature* 430 (2004) 539.
- [11] C. C. Homes, S. V. Dordevic, D. A. Bonn, R. Liang, W. N. Hardy, T. Timusk, *Phys. Rev. B* 71 (2005) 184515.
- [12] C. C. Homes, S. V. Dordevic, T. Valla, M. Strongin, *Phys. Rev. B* 72 (2005) 134517.

- [13] D. Y. Smith, Dispersion theory, sum rules, and their application to the analysis of optical data, in: E. D. Palik (Ed.), Handbook of Optical Constants of Solids, Academic, New York, 1985, pp. 35–68.
- [14] R. A. Ferrell, R. E. Glover, III, Phys. Rev. 109 (1958) 1398.
- [15] M. Tinkham, R. A. Ferrell, Phys. Rev. Lett. 2 (1959) 331.
- [16] D. N. Basov, S. I. Woods, A. S. Katz, E. J. Singley, R. C. Dynes, M. Xu, D. G. Hinks, C. C. Homes, M. Strongin, Science 283 (1999) 49.
- [17] For simplicity, all units are in cm^{-1} ; to achieve this two unit conversions are implicitly employed in the text; $1 \text{ cm}^{-1} = (\pi/15) \Omega^{-1}\text{cm}^{-1}$ and $1 \text{ cm}^{-1} = 1.44 \text{ K}$.
- [18] Z. Shen, D. S. Dessau, B. O. Wells, D. M. King, W. E. Spicer, A. J. Arko, D. Marshall, L. W. Lombardo, A. Kapitulnik, P. Dickinson, S. Doniach, J. DiCarlo, T. Loeser, C. H. Park, Phys. Rev. Lett. 70 (1993) 1553.
- [19] W. N. Hardy, D. A. Bonn, D. C. Morgan, R. Liang, K. Zhang, Phys. Rev. Lett. 70 (1993) 3999.
- [20] D. W. Lynch, W. R. Hunter, An introduction to the data for several metals, in: E. D. Palik (Ed.), Handbook of Optical Constants of Solids II, Academic Press, San Diego, 1991, p. 396.
- [21] W. Zimmerman, E. H. Brandt, M. Bauer, E. Seider, L. Genzel, Physica C 183 (1991) 99.
- [22] C. Varmazis, M. Strongin, Phys. Rev. B 10 (1974) 1885.
- [23] O. Klein, E. J. Nicol, K. Holczer, G. Grüner, Phys. Rev. B 50 (1994) 6307.
- [24] A. V. Pronin, M. Dressel, A. Pimonev, A. Loidl, I. V. Roshchin, L. H. Greene, Phys. Rev. B 57 (1998) 14416.

- [25] R. A. Smith, V. Ambegaokar, Phys. Rev. B 45 (1992) 2463, in the absence of weak localization, in the dirty limit $\Gamma \gg \Delta$, it was shown that $\rho_s = 4\pi^2\sigma_{dc}\Delta \tanh[\Delta/2T]$, where σ_{dc} is the dc conductivity in the normal state and Δ is the superconducting energy gap. Assuming that the gap scales with T_c and that $T \ll T_c$, then $\rho_s \propto \sigma_{dc}T_c$.
- [26] J. Orenstein, G. A. Thomas, A. J. Millis, S. L. Cooper, D. H. Rapkine, T. Timusk, L. F. Schneemeyer, J. V. Waszczak, Phys. Rev. B 42 (1990) 6342.
- [27] J. Zaanen, Nature 430 (2004) 512.
- [28] E. Schachinger, J. P. Carbotte, Phys. Rev. B 67 (2003) 134509.
- [29] S. L. Cooper, K. E. Gray, Anisotropy and interlayer coupling in the High- T_c cuprates, in: D. M. Ginsberg (Ed.), Physical Properties of High-Temperature Superconductors IV, World Scientific, Singapore, 1994, pp. 61–188.
- [30] D. Mihailovic, Phys. Rev. Lett. 94 (2005) 207001.

Fig. 1. The log-log plot of the spectral weight of the condensate N_c vs $\sigma_{dc} T_c$ of the hole-doped copper-oxide superconductors for pure and Pr-doped $\text{YBa}_2\text{Cu}_3\text{O}_{6+x}$; pure and Zn-doped $\text{YBa}_2\text{Cu}_4\text{O}_8$; pure and Y/Pb-doped $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$; underdoped $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$; $\text{Tl}_2\text{Ba}_2\text{CuO}_{6+\delta}$; electron-doped $(\text{Nd,Pr})_{2-x}\text{Ce}_x\text{CuO}_4$ and the bismuth oxide material $\text{Bi}_{1-x}\text{K}_x\text{BiO}_3$. Within error, all the points may be described by a single (dashed) line, $N_c \simeq 4.4 \sigma_{dc} T_c$; the upper and lower dotted lines represent approximately the spread of the data. (The values used in the plot are shown in Table I of Ref. [12].)

Fig. 2. The log-log plot of the predicted behavior from the BCS model of the spectral weight of the condensate N_c in Nb for a wide range of scattering rates $1/\tau = 0.05\Delta \rightarrow 50\Delta$, and assuming a plasma frequency $\omega_p = 56\,000 \text{ cm}^{-1}$, critical temperature $T_c = 9.2 \text{ K}$ and an energy gap of $2\Delta = 3.5 k_B T_c$ (solid line). The dashed line indicates $1/\tau = 2\Delta$. To the right of this line the material approaches the clean limit with a residual resistance ratio (RRR) of $\gtrsim 100$; the right arrow indicates that for larger RRR's, σ_{dc} close to T_c increases, but N_c has saturated to $\omega_p^2/8$ (or $\rho_s \rightarrow \omega_p^2$; the data point for Nb in this regime is from Ref. [22]). As the scattering rate increases, the spectral weight of the condensate adopts a linear scaling behavior (dotted line); the two points for Nb (Refs. [23,24]) shown in Fig. 1 lie close to this line, indicating that they are in the dirty limit. The scaling relation shown in Fig. 1 (dash-dot line) is slightly offset from the BCS dirty-limit result.

Fig. 3. The optical conductivity for the BCS model in the normal (solid line) and superconducting states (dashed line) for a material in the clean limit ($1/\tau \ll 2\Delta$). The normal-state conductivity is a Lorentzian centered at zero frequency with a full width at half maximum of $1/\tau$ for $T \simeq T_c$. The spectral weight associated with the formation of a superconducting condensate is indicated by the hatched area. The majority of spectral weight lies below 2Δ . Inset: $N_n \equiv N(\omega, T \simeq T_c)$ (solid line), $N_s \equiv N(\omega, T \ll T_c)$ (dashed line), and difference between the two $N_c = N_n - N_s$ (long-dashed line) normalized with respect to $\rho_s/8$; $8 N_c/\rho_s$ converges rapidly to unity and is fully formed at energies comparable to $1/\tau$.

Fig. 4. The optical conductivity for the BCS model in the normal (solid line) and superconducting states (dashed line) for a material in the dirty limit ($1/\tau \gtrsim 2\Delta$). The spectral weight associated with the formation of a superconducting condensate is indicated by the hatched area. A significant amount of spectral weight lies above 2Δ . Inset: $N_n \equiv N(\omega, T \simeq T_c)$ (solid line), $N_s \equiv N(\omega, T \ll T_c)$ (dashed line), and difference between the two $N_c = N_n - N_s$ (long-dashed line) normalized with respect to $\rho_s/8$; $8 N_c/\rho_s$ converges at energies comparable to 4Δ .

Fig. 5. The log-log plot of the spectral weight of the condensate N_c vs $\sigma_{dc} T_c$ for the a - b planes and the c axis for a variety of cuprates. Within error, all of the points fall on the same universal (dashed) line defined by $N_c \simeq 4.4 \sigma_{dc} T_c$; the dotted line is the dirty limit result $N_c \simeq 8.1 \sigma_{dc} T_c$ for the BCS weak-coupling case ($2\Delta = 3.5 k_B T_c$) from Fig. 2, and also represents the Josephson result for the BCS weak-coupling case, used to describe the scaling along the c -axis [11]. The subscripts for the c -axis data points indicate different chemical dopings. (Values for the c -axis points are listed in the supplemental information of Ref. [10].)

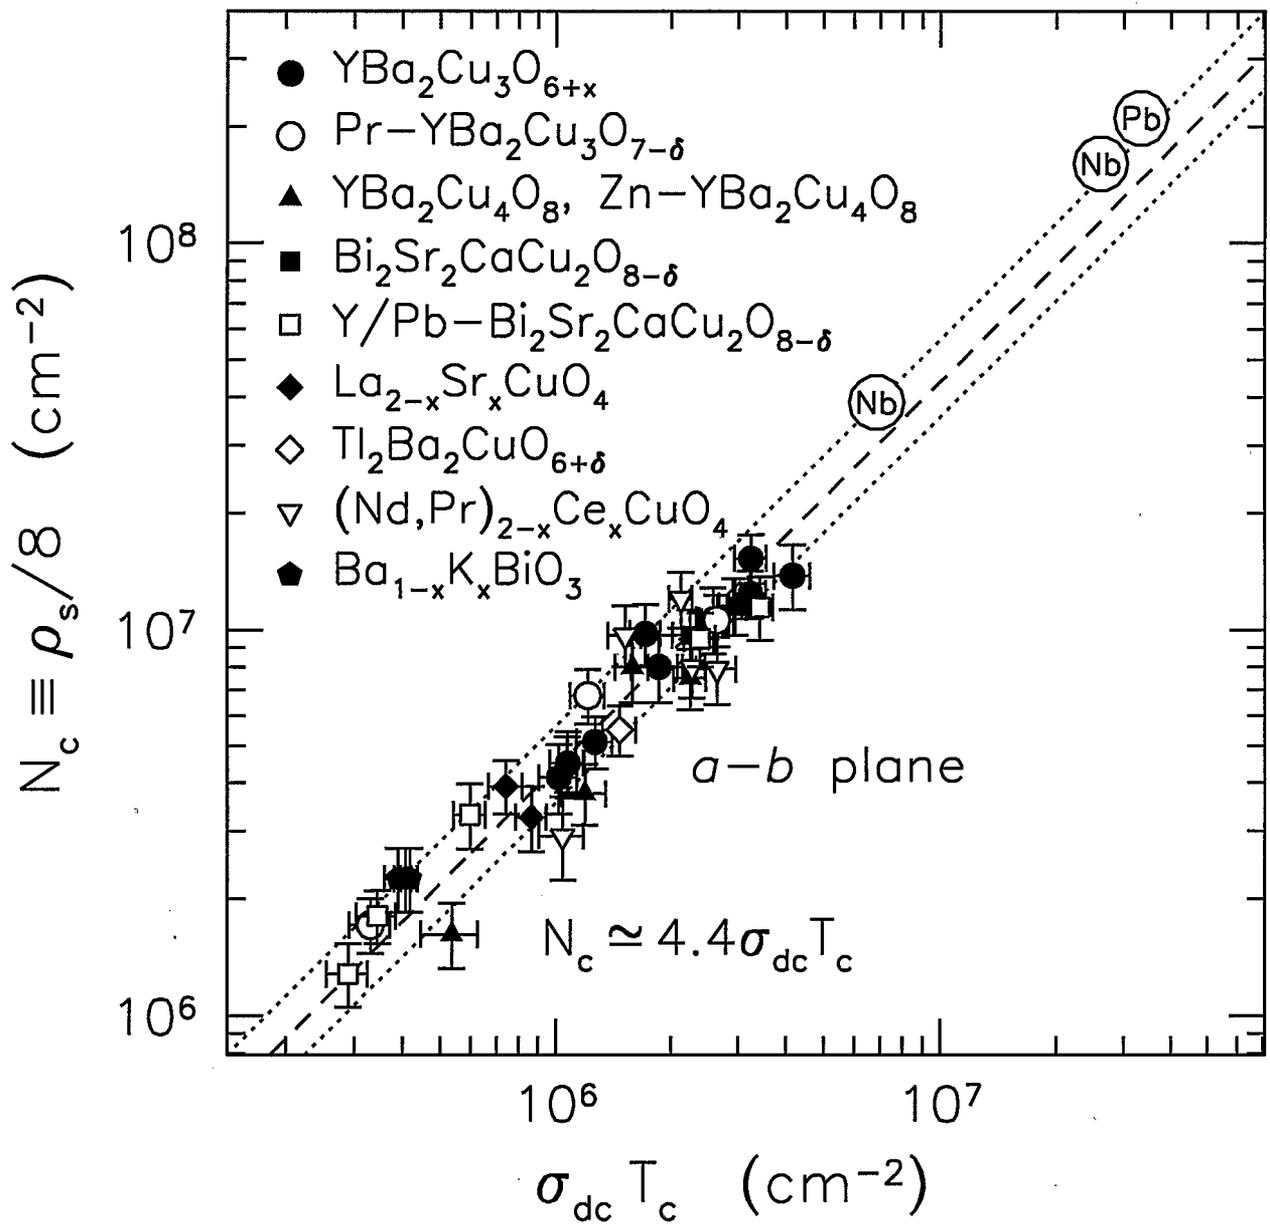


Figure 1 / C.C. Homes / PC-02INV

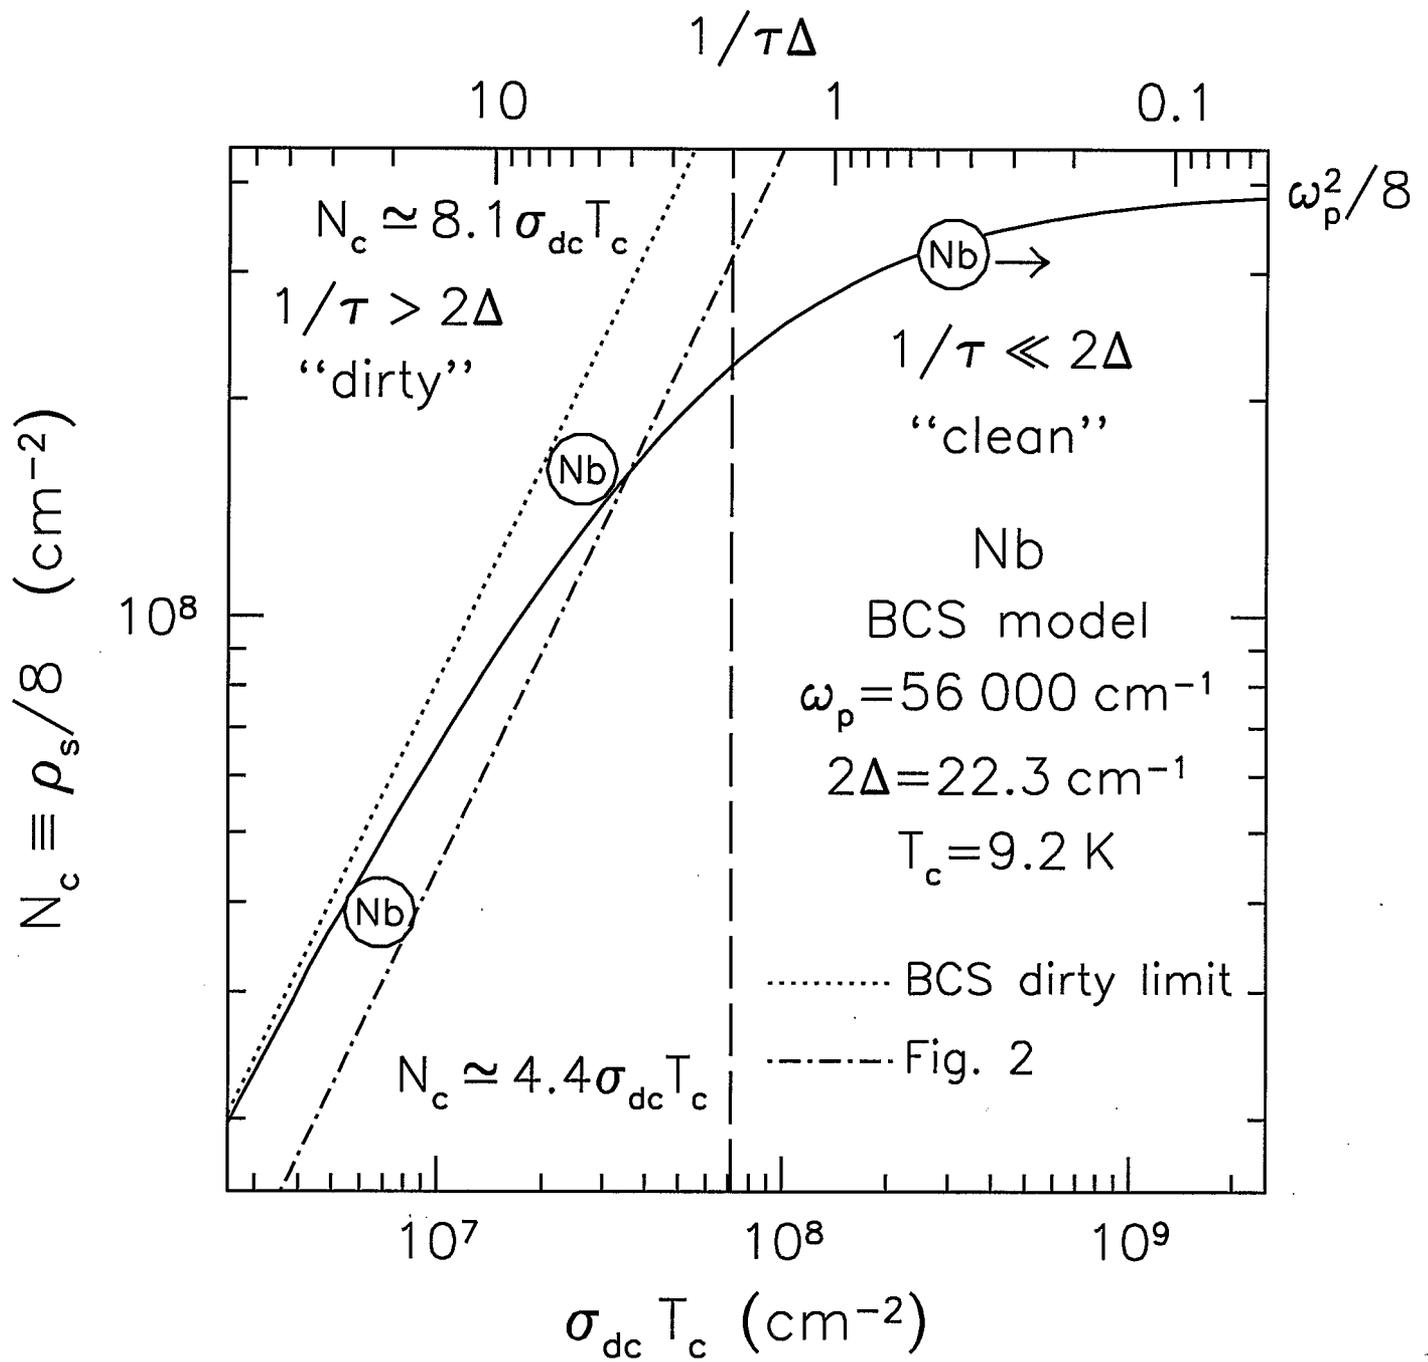


Figure 2 / C.C. Homes / PC-02INV

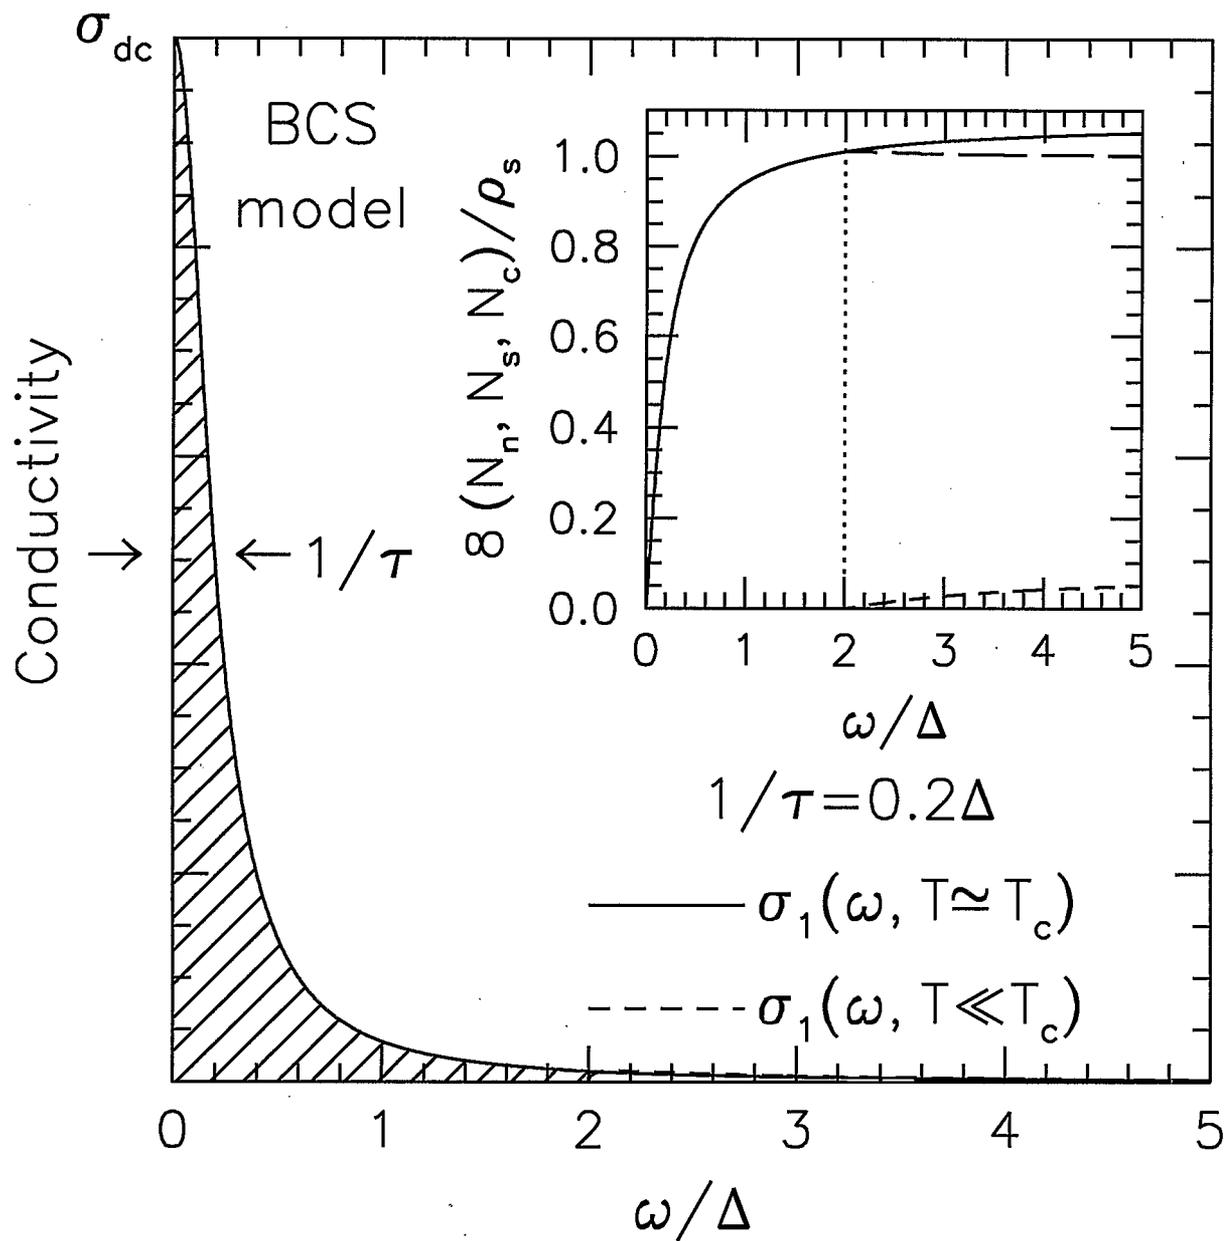


Figure 3 / C.C. Homes / PC-02INV

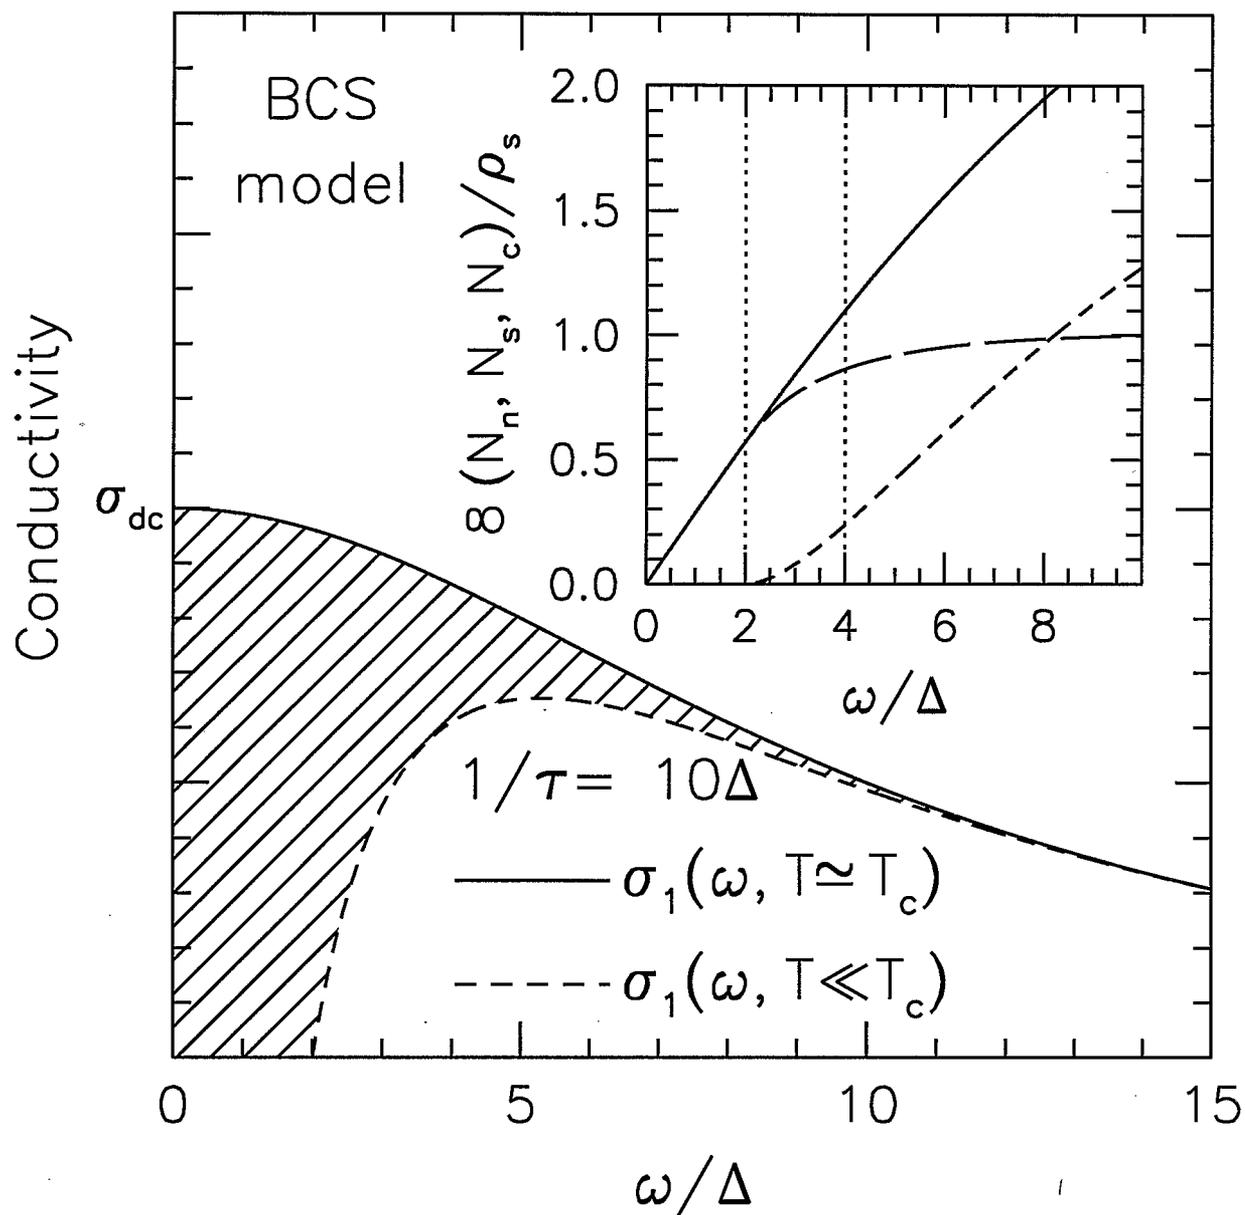


Figure 4 / C.C. Homes / PC-02INV

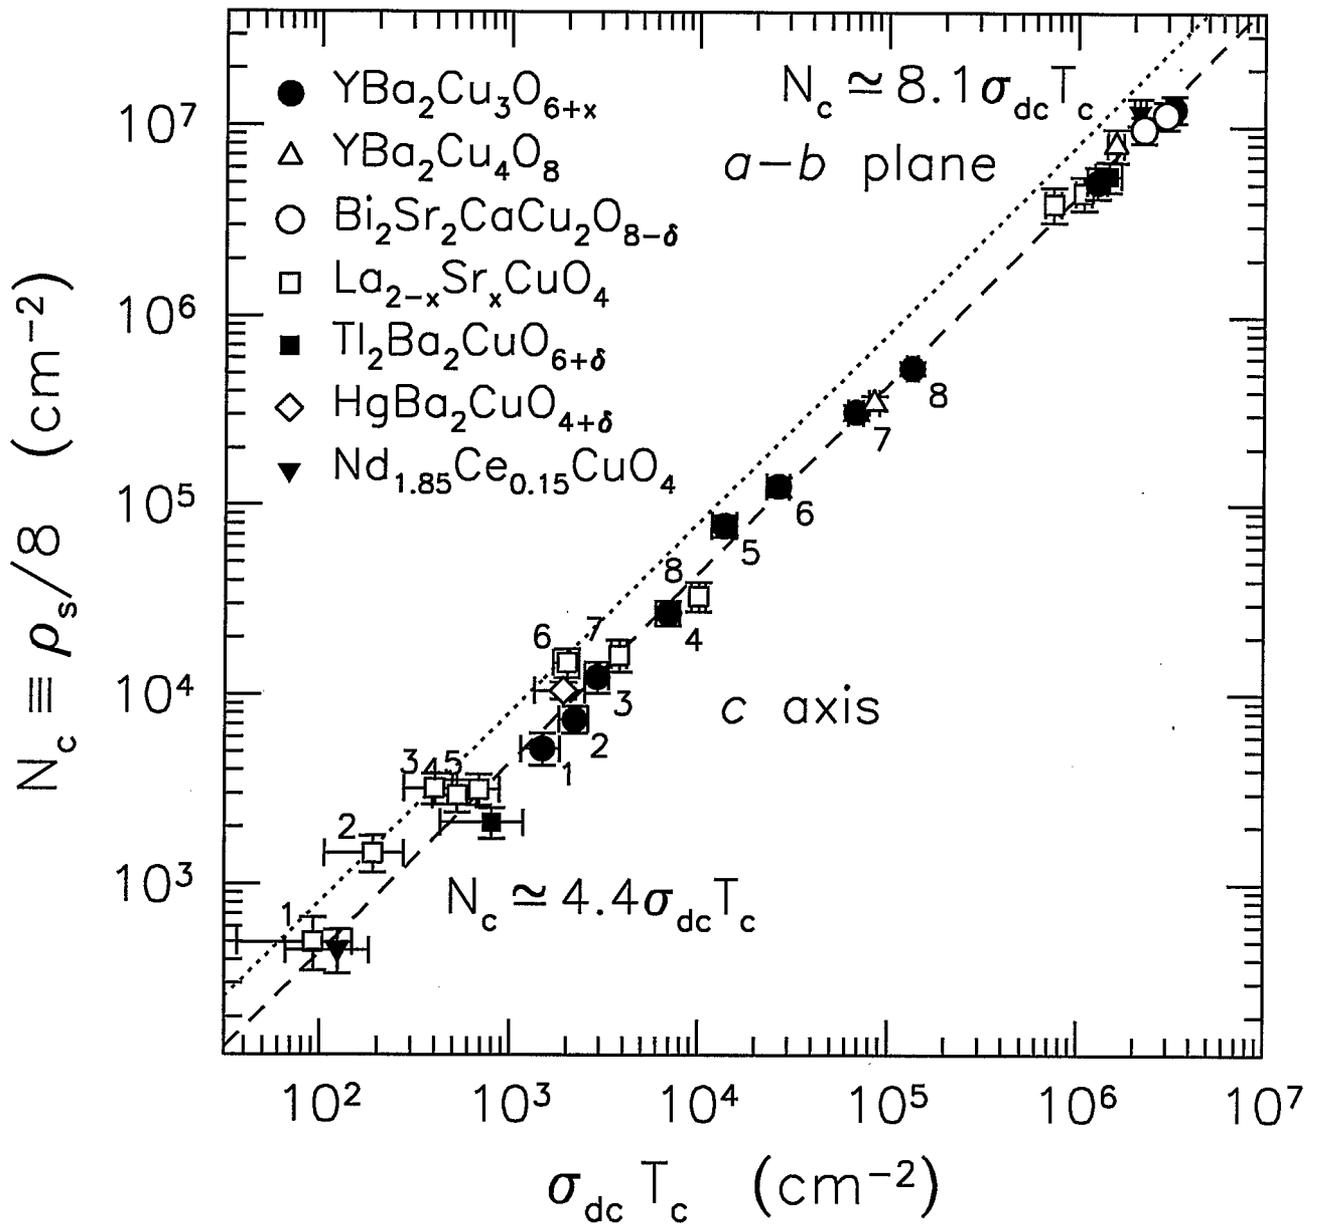


Figure 5 / C.C. Homes / PC-02INV